



STUDY THE OPTICAL PROPERTIES OF BIODEGRADABLE POLYLACTIC ACID / SILVER NANOCOMPOSITES

Nadia Abbas Ali

University of Baghdad, College of Science, Department of Physics Baghdad, Iraq

*Corresponding author email:

ABSTRACT

In this experiment nano silver added to the biodegradable polylactic acid and prepared by casting method at room temperature and thickness (120 μ m) at different concentration of nano silver powder. Optical properties have been measured in the range of (300-800) nm. The electronic transition in pure polylactic acid (PLA) and PLA/Ag nanocomposites indicated direct allowed transition. It is found that the energy gap of polylactic acid is 3.3eV and this value decreased within range of (3.3-2.7) eV when the concentration of nano silver powder increased from (2, 4, and 6%) respectively. The optical constants which include the refractive index (n), real (ϵ_1) and imaginary (ϵ_2) part of dielectric constant calculated at $\lambda = 550$ nm and find it decreased with increasing of nano silver.

KEY WORDS: biodegradable polylactic acid, nano silver, optical properties, energy gap.

INTRODUCTION

Biodegradable polymers were first introduced in 1980s. Polymers from renewable resources have attracted an increasing amount of attention over the last two decades, predominantly due to two major reasons: firstly environmental concerns, and secondly the realization that our petroleum resources are finite. There are many sources of biodegradable plastics, from synthetic to natural polymers. Natural polymers are available in large quantities from renewable sources, while synthetic polymers are produced from non-renewable petroleum resources. Biodegradation of polymeric biomaterials involves cleavage of hydrolytically or enzymatically sensitive bonds in the polymer leading to polymer erosion.^[1,2] Polylactic acid (PLA) is prominent among the polymers that are biodegradable and biocompatible due to versatility of its applications and relatively low cost of production at industrial scale. PLA, is linear aliphatic thermoplastic polyester, produced from renewable resources, has several attractive properties such as biocompatibility, high strength, and thermo plasticity. It has been used in medical applications, such as surgical sutures, implants, tissue culture, and controlled drug delivery, the high stiffness and brittleness at ambient temperatures associated with PLA must be improved to allow for more applications such as packaging food^[3,4,5]. Polylactide (PLA) have been known for several decades but only recently have these polymers gained commercial significance as a leading environmentally benign plastic available from renewable resources. Therefore, it is highly desirable to understand the optical properties of these materials so that they can be manipulated to develop materials of desirable characteristics for a specific objective. Optical properties such as color, clarity, and refractive index are important in dyeing operations for textile and in various packaging applications^[6,7]. The absorption and transmission of light by polymers is

especially important in the food packaging industry where the packaged goods are light sensitive. Another issue in fresh food packaging is the effect of irradiation in the package since ultraviolet light irradiation is a common method used for lowering microbial population in foods^[8,9]. Transparent materials are materials that allow one or more of the frequencies of visible light to be transmitted through them. Several important parameters are currently used to characterize visible light transmission and color of plastics, such as transparency. This is defined as the transmission of visible light in the 540–560 nm range. The average transparency of food packaging films is around 95%^[10,11]. Refractive index is a fundamental physical property of a substance that is often used for its identification, to confirm its purity or to measure its concentration. By definition, the refractive index of a medium is a measure of how much the speed of light is reduced inside the medium. It is a fundamental optical property of polymers that is directly related to other optical, electrical, and magnetic properties. Knowledge about this property is valuable due to its application in the design of new optical polymeric materials. The addition of nanosized inorganic or organic dopants to polymers allows the modification of the polymers' physical properties enabling the realization of functionalized polymers with new application fields, for example, in microoptics^[12].

OPTICAL ENERGY GAP

The experimental results on optical absorption in glassy materials have been reported by Mott and Davis^[13,14]. One important difference between amorphous and crystalline solids is that; in the crystalline nonmetallic solids, there is a sharp well defined lattice absorption edge and energy gap (E_g) given by the relation :

$$E_g = hc / \lambda \quad (1)$$

Where: E_g =energy gap, h = Planks constant, c =velocity of light, λ =wavelength.

The absorption coefficient (α) which is defined as the decrement ratio of incident radiation relative to unit length in the direction of wave propagation inside the medium is relating with the absorbance (A) through the relation:-

$$\alpha = \frac{2.303A}{t} \quad (2)$$

Where: (t) is the thickness of sample.

Many researchers put the empirical equation between the optical energy gap(E_g) and energy of the incident photon which is :-

$$(h\nu) = B(h\nu - E_g)^r \quad (3)$$

Where B is proportion with the inverse of amorphousity, ($h\nu$) is the energy of incident photon, which can be calculated using the equation:-

$$h\nu = \frac{1240}{\lambda \text{ (nm)}} \quad (4)$$

r is the order of the optical transition depending on the nature of electronic transition .The transition is called direct if the extremities of V.B and C.B lie at the same K-space, while the transition is called indirect if the transition possible only with phonon assisted ($\Delta E \neq 0$). Thus the value of r may be 1/2,2,3/2, and 3 corresponding to the allowed direct ,allowed indirect, forbidden direct and forbidden indirect transition respectively. The

extinction coefficient (K) (imaginary part of the refractive index) can be calculated by the relation:

$$k = \frac{K}{4K} \quad (5)$$

The refractive index (n) can be measured (when the reflectance (R) and (k) are known) by using the equation (6), Where (n) is the refractive index given by:

$$n = \left[\frac{(1+R)^2}{(1-R)^2} - (k^2 - 1) \right]^{1/2} + \frac{1+R}{1-R} \quad (6)$$

R is the reflectance and given by equation:

$$R = \frac{(n-1)^2 + k^2}{(n+1)^2 + k^2} \quad (7)$$

The dielectric (ϵ) is the complex dielectric constant can be introduced by:

$$\epsilon = \epsilon_1 - i\epsilon_2 \quad (8)$$

The parameter ϵ_1 is the real part of dielectric constant, ϵ_2 is the imaginary part of dielectric constant, from equations (7) and (8) one can obtain:

$$\epsilon_1 = n^2 - k^2 \dots \quad (9)$$

$$\epsilon_2 = 2nk \quad (10)$$

Experimental details

Lactic acid (99.9%), Tin chloride dehydrated ($\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$) P-toluene sulfonic acid (TSA), Methylene Chloride. Nano silver with particle size (13.69 nm) is shown in Fig (1) measured of nan Ag.

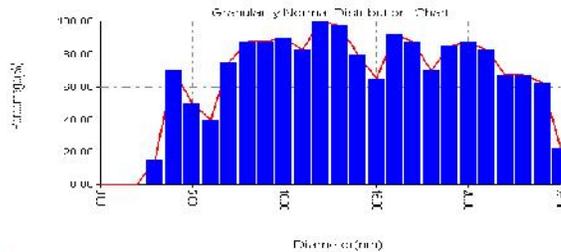


FIGURE 1: Granularity normal distribution chart for nano Ag

Preparation of pure PLA and PLA/silver nanocomposites

100 gm of lactic acid was mixed with methylene chloride for 5hrs at reflux temperature without any catalyst .After the removal of water of the condenser, the reaction vessel was cooled at 50°C, the required amount of catalyst $\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$ (0.5wt%), TSA (0.4wt%) were add and this was followed by slow heating of the reaction mixture to the refluxing temperature of the solvent under mild stirring with the help of magnetic stirring bar. The temperature gradually increased to 160°C in 3 hrs, and the reaction mixture was stirred continuously. Polymerizations are done at 120-160°C for 5hrs .At the end of the reaction, the flask was cooled, and the product was dissolved in chloroform and subsequently precipitated in methanol.

The resulting solid was filtered and dried Under vacuum at 60°C under vacuum for 24hrs .

Powder PLA weighted grade (1wt %) dissolved in chloroform to obtain 20 wt% solution of PLA by slowly in 60°C for 2 hours and cast on glass plates. PLA/ nano silver composite films were prepared by different weight percentages (2, 4 and 6%) nano silver and swollen in chloroform by mixing for 2 hours while polylactic acid dissolved in chloroform then nano solution were mixed by shearing mixer at 800 rpm for one hour to have good distribution and less agglomeration. Then cast on the glass plates and then kept at 60°C in the vacuum oven for 24 hour to ensure complete solvent removal. The thickness of PLA/ silver nanocomposite thickness of 120 μm .

UV-Vis Spectrophotometer

The UV- visible spectra recorded with the help of SHIMADZU UV- in range (300–800) nm. UV spectra gave information about transmission of pure PLA, and PLA/Ag nanocomposites .

RESULTS & DISCUSSION

Transmission of pure PLA and PLA/Ag nano composites

Fig (2) shows the variation of transmission as a function of wavelength of pure PLA at UV region is 70% and 87% at visible region .It can be observed from this figures that the transmission increase with increasing of () for all Ag

contact this revealed to the smooth reflecting surfaces of the samples and there was not much scattering loss at the surface.

In PLA/Ag nanocomposites transparency is an effective index for providing information on the size of dispersed particles in the polymer matrix, typically observing aggregate domains larger than visible wavelength could obstruct light, leading to translucent or opaque films while highly dispersed nanoparticles in a transparent polymer matrix result in optically clear nanocomposites in visible light given that the size of particles is smaller than the wavelength. At shows in Table (1) the transmission at UV and visible spectra (300–800) nm wavelength.

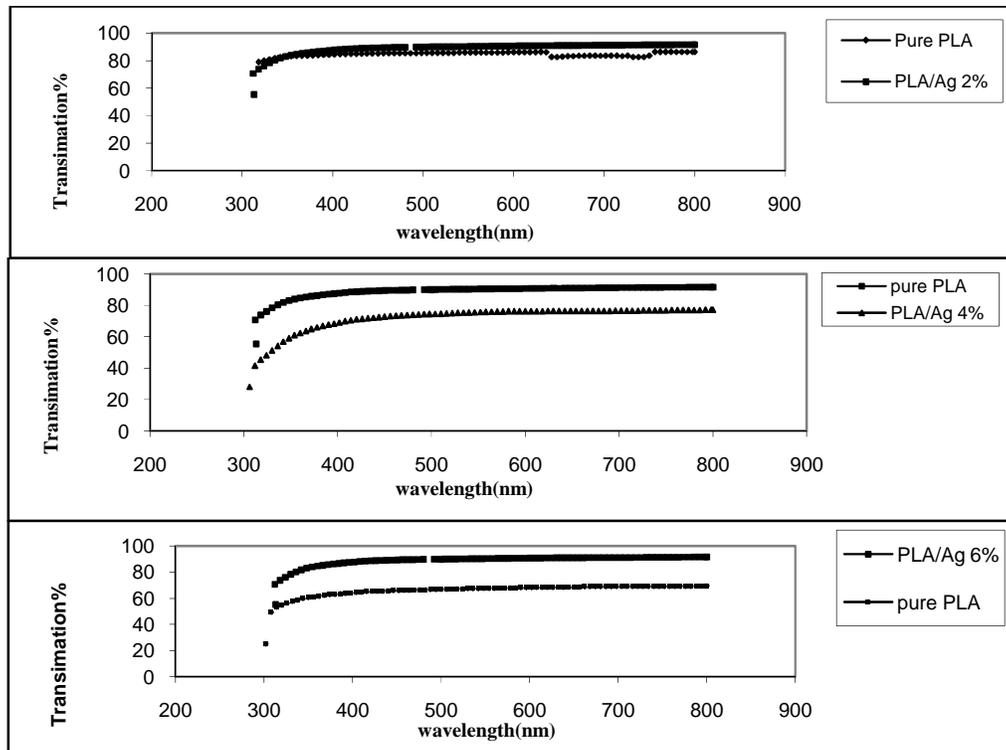


FIGURE 2: Transmittance as function to wavelength for PLA, PLA/Ag nanocomposites

In the visible range (400-700 nm), each wavelength causes a particular sensation of color as the eye is not equally sensitive to light emitted at all wavelength, the transparency of plastic sheeting is defined as the transmission of visible light in the short range of 540-560 nm. The measurement of the transmission percentage at

550 nm reveals that all substrates are transparent with around 87 % for the pure PLA that show the highest transmittance, around 80% transmittance for the PLA/Ag at 2% samples and around 70% transmittance for PLA/Ag at 4% and 65% for PLA/Ag at 6 % (Table 1).

TABLES 1: UV –VIS Transmission at selected wavelength (300 and 550) nm of pure PLA and PLA/Ag nanocomposites

Samples	Transmission in UV at 300 nm %	Transmission in Visible at 550 nm %
Pure PLA	70	87
PLA/Ag2%	68	80
PLA/Ag 4%	40	70
PLA/Ag 6%	50	65

Optical energy gap

Fig (3) represent the optical energy gap for pure PLA and PLA/Ag nanocomposites, for the pure PLA the band was (3.3) eV and decreased from (3.3-2.7) eV this indicated

that allowed direct transition is involved which is due to – * transition. The experimental results to calculate the energy gap according to Taucze relation, indicate that the electronic transition for these polymer equal to (r=1/2).

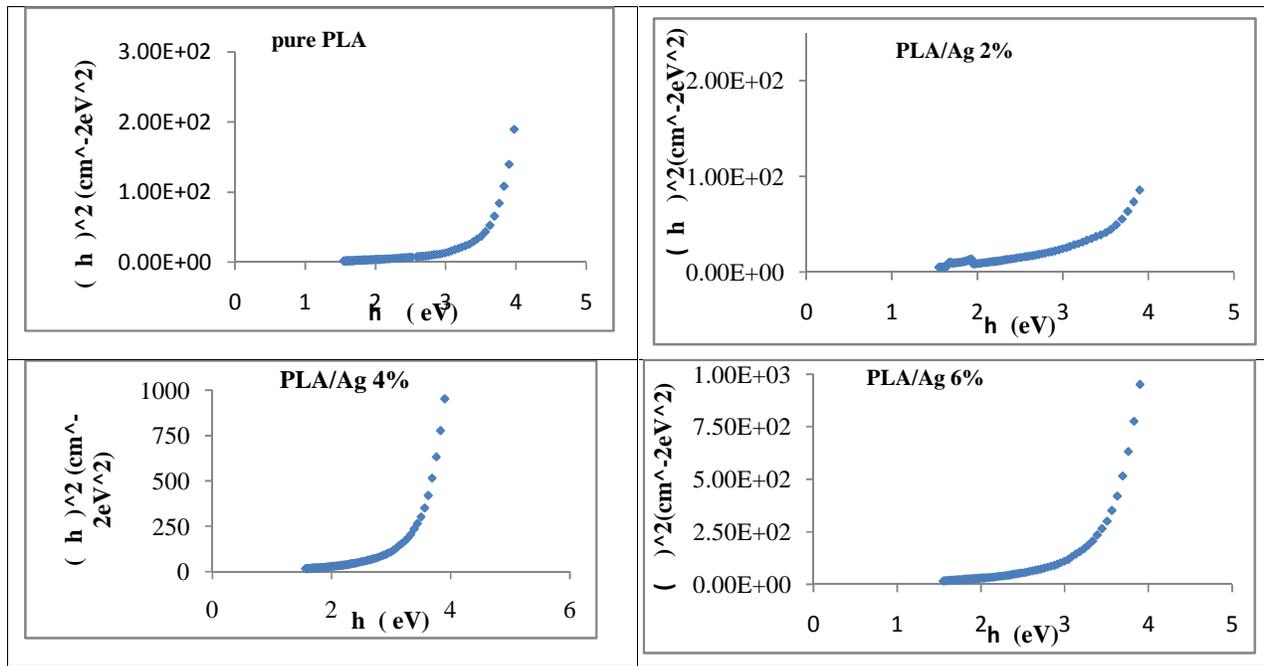


FIGURE 3: The variation of $(h)^2$ versus (h) for pure PLA and PLA/Ag nanocomposites

OPTICAL CONSTANT

The optical constants (n_1, n_2) were determined from both the transmittance (T) and absorbance (A).

Fig (4) shows the variation of reactive index (n) for PLA and PLA/Ag nanocomposites calculated from eq.(6) it is

found that the values of refractive index decreasing slightly with increasing (h) from (2.65-2.1) this behavior can be explained on the basic of that increasing silver (lowering the packing density) which in turn increase propagation velocity of light through them.

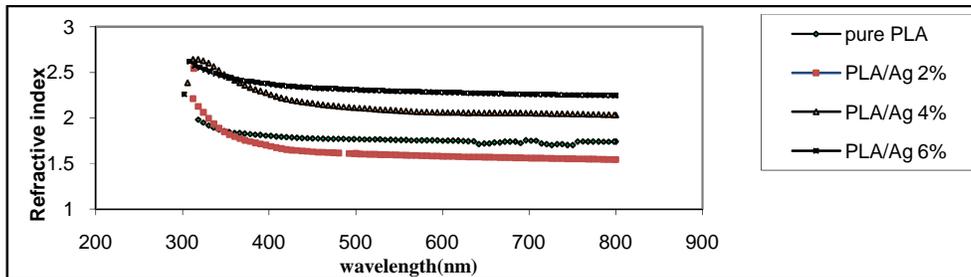


FIGURE 4: The variation of refractive index (n) versus wavelength for PLA and PLA/Ag nanocomposites

The dielectric constant of real part (ϵ_1) and imaginary part (ϵ_2) which depend on the frequency of the electromagnetic waves. The variation of (ϵ_1) (ϵ_2) with the wavelength of the incident radiation is due to the change of reflectance and absorbance .It can observe that the variation of ϵ_1 has

similar trend to the variation of (n) because of smaller values of k^2 in comparison with n^2 , where $\epsilon_1 = n^2 - k^2$ while the variation of ϵ_2 mainly depends on the variation of k values which are related to the variation of ϵ_1 , where $\epsilon_2 = 2nk$

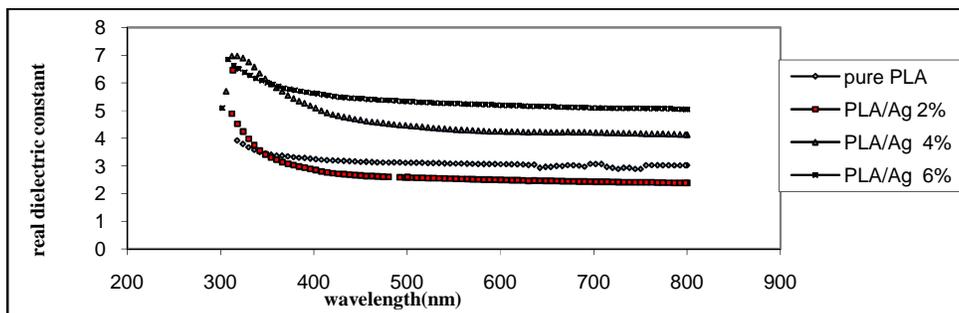


FIGURE 5: The variation of real part of dielectric constant (ϵ_1) for PLA and PLA/Ag nanocomposites

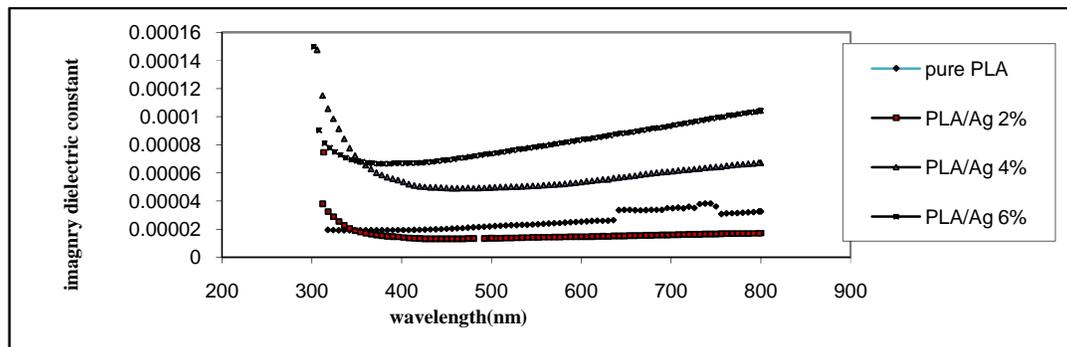


FIGURE 6: The variation of imaginary part (ϵ_2) versus wavelength for PLA and PLA/Ag nanocomposites

CONCLUSION

- 1- Optical properties have been measured in the range of (300-800) nm to prepare PLA/Ag nanocomposites from (2, 4, and 6%) respectively.
- 2- The electronic transition in pure polylactic acid (PLA) and PLA/Ag nanocomposites indicated direct allowed transition
- 3- The energy gap of polylactic acid is 3.3 eV and this value decreased within a range of (3.3-2.7) eV when the concentration of nano silver increased
- 4- optical constants which include the refractive index (n), real (ϵ_1) and imaginary (ϵ_2) part of dielectric constant calculated at $\lambda = 550$ nm and found it decreased with increasing of nano silver

Future Work

- 1-Study of additive another nano particle and show effect in optical properties.
- 2-study the electrical properties of PLA/Ag nanocomposites.

REFERENCES

- [1]. Sangale, M.K., Shah Nawaz, M. and Ade, A.B. (2012) "A review on Biodegradation of Polythene: The Microbial Approach". *Journal of Bioremediation and Biodegradation* (3) 164.
- [2]. Yutaka Tokiwa, Buenaventura, P. Calabia, Charles U. Ugwu and Seiichi Aiba (2009) "Biodegradability of Plastics" *Int. J. Mol. Sci.*, 10, 3722-3742.
- [3]. Manika Sharma, Pratibha Sharma, Anima Sharma and Subhash Chandra (2015) microbial degradation of Plastic- A Brief Review "Journal of Microbiology", 4 (1).
- [4]. Kavitha, R., Anju, K. Mohanan and Bhuvaneshwari, V. (2014) "Biodegradation of low density polyethylene by bacteria isolated from oil contaminated soil. *International Journal of Plant, Animal and Environmental Sciences* ISSN 2231-4490.
- [5]. Mathew, A.P., Oksman, K. and Sain, M. (2015) "Mechanical properties of biodegradable composites from poly lactic acid (PLA) and microcrystalline cellulose (MCC)," *Journal of Applied Polymer Science*, vol. 97, no. 5, pp. 2014–2025.
- [6]. Sandeep, S. Laxmeshwar, Viveka. S., Madhu Kumar. D.J. and Nagaraja. G.K. (2012) Preparation and properties of composite films from modified cellulose fibre-reinforced with PLA," *Der Pharma Chemica*, 4 (1):159-168.
- [7]. Lisman Suryanegara, Antonio Norio Nakagaito, Hiroyuki Yano (2009) "The effect of crystallization of PLA on the thermal and mechanical properties of microfibrillated cellulose-reinforced PLA composites" *Composites Science and Technology*, V. 69, Issues 7–8, P. 1187–1192.
- [8]. Sandeep, S. Laxmeshwar, Viveka. S., Madhu Kumar. D. J. and Nagaraja. G.K. (2012) Preparation and properties of composite films from modified cellulose fibre-reinforced with PLA," *Der Pharma Chemica*, 4 (1):159-168.
- [9]. Cardoso, J.J.F., Queirós, Y.C., Machado, K.J.A., Costa, J.M., Ucas, F.E. (2013) synthesis, characterization, and in vitro degradation of poly(lactic acid) under petroleum production conditions" *Brazilian journal of petroleum and gas* v. 7 n. 2, 057-069
- [10]. R.M. Izan, Robert, A.S. Ing, K. (2011) Melting Behaviour and Dynamic Mechanical Properties of Poly(lactic acid)-Hemp-Nanosilica Composites", *Asian Transactions on Basic and Applied Sciences* ,Vol.3 Issue 2, 556-561.
- [11]. Fina, F. Geobaldo, A. Venturello, G. Camino, Fukushima, (2012) Properties of polylactic acid nanocomposites based on montmorillonite, sepiolite and zirconium phosphonate" *eXPRESS Polymer Letters* Vol.6, No.11, pp.914–926.
- [12]. Norio Nakayama, C.J., Grande, F.G. Torres, C M Gomez, O .P Troncoso, J Canet-Ferrer and J .Martinez- Pastor, Toyoharu Hayashi 2008,"Preparation and characterization of poly (L-lactic acid)/ TiO₂ nanoparticle nanocomposite films with high transparency and efficient photodegradability "Polymer Degradation and Stability *Composites* 16, 181
- [13]. Studies Majid Jamshidian, Elmira Arab Tehrani, Muhammad Imran, Muriel Jacquot, and St'ephane (2010) ,"Poly-Lactic Acid: Production, Applications, Nanocomposites, and Release Desobry *Comprehensive Reviews in Food Science and Food Safety*, Vol.9.
- [14]. Lim, L.T., R. Auras, Rubino, M. (2008) Processing technologies for poly(lactic acid)", *Science* ,Vol., pp. 820–852.